

See discussions, stats, and author profiles for this publication at: <https://www.researchgate.net/publication/305472878>

Characterization of SnO₂ Sensors Nanomaterials by Polarization Modulation Method

Chapter · January 2016

DOI: 10.1007/978-94-017-7593-9_20

CITATIONS

0

READS

23

7 authors, including:



Liudmila Filevska

Odessa National University

37 PUBLICATIONS 33 CITATIONS

[SEE PROFILE](#)



V. Smyntyna

Odessa National University

275 PUBLICATIONS 598 CITATIONS

[SEE PROFILE](#)



Maksym Stetsenko

National Academy of Sciences of Ukraine

21 PUBLICATIONS 14 CITATIONS

[SEE PROFILE](#)



S. P. Rudenko

National Academy of Sciences of Ukraine

38 PUBLICATIONS 90 CITATIONS

[SEE PROFILE](#)

Some of the authors of this publication are also working on these related projects:



13. Coordinator of BIOSENSORS Agricult - FP7-PEOPLES-2012-IRSES project, contract Nr.316177 - "DEVELOPMENT OF NANOTECHNOLOGY BASED BIOSENSORS FOR AGRICULTURE", 01.09.2012-31.08.2016. [View project](#)



Detection of optical polarization properties of zeolite (zeolite with metal nanoparticle) thin films by modulation polarimetry [View project](#)

All content following this page was uploaded by [V. Smyntyna](#) on 29 November 2016.

The user has requested enhancement of the downloaded file.

Chapter 20

Characterization of SnO₂ Sensors

Nanomaterials by Polarization Modulation Method

V.S. Grinevych, L.M. Filevska, V.A. Smyntyna, M.O. Stetsenko, S.P. Rudenko, L.S. Maksimenko, and B.K. Serdega

Abstract The polarization characteristics for tin dioxide cluster films are studied by the method of modulation polarization spectroscopy. The galvanic conductivity presence in the films is the basis for registration in it the surface plasmon resonances. The spectral characteristics analysis by means of expansion in terms of Gauss components for the Stocks vector Q component of the probe radiation gave the parameters of the revealed resonances. The resonance excitation of polaritons and localized surface plasmons is established. The dispersion characteristics of non-radiative modes of surface plasmons are obtained which matches the cluster film structure. The numerical values comparison for resonances relaxation constants leads to the conclusion of application of one of them in sensors.

20.1 Introduction

The unique chemical resistance in an aggressive medium, specific adsorptive-catalytic, electrophysical and optical properties, cheapness in production and possibility to create Tin dioxide nano size forms secures its leading position among materials used for ecological monitoring [1, 2]. Nevertheless it is not the only sphere for application of this material. The resistance sharp decrease property for sensitive elements based on SnO₂ films at pressure decrease is successfully used in pressure transducers [2]. The conductive SnO₂ films are actively used as transparent electrodes in sun cells [3].

V.S. Grinevych (✉) • L.M. Filevska • V.A. Smyntyna
Department of Experimental Physics II. Mechnikov, Odessa National University (ONU),
Dvoryanskaya str., Odessa 65082, Ukraine
e-mail: grinevich@onu.edu.ua

M.O. Stetsenko • S.P. Rudenko • L.S. Maksimenko • B.K. Serdega
V.E. Lashkarev Institute of Semiconductors Physics, National Academy of Sciences of Ukraine
(NASU) Nauky Prospect, 45, Kyiv 03680, Ukraine

The nonstoichiometric oxides, SnO_x is among them, may become the basic material in the nearest future for new elements of computer energy independent memory-memristors, which modify their electric resistance under the current influence [4]. The application of nanoparticles of the dioxide composite material built in graphene nanoribbons, as anodes in Lithium Ions batteries in mobile electron technique were recently reported [5]. This may seriously enhance the productivity and effectiveness of such batteries and to achieve high initial charge and discharge potentials [6].

The use of optical methods of gas and biological objects detection in liquid and gaseous mediums became the new stage in nanosized tin dioxide application [7].

The tin-dioxide physical properties are principally dependent on the methods of its production. Among them are expensive ion-plasma, electron – beam deposition, magnetron spray and more cheap chemical methods – electric spray pyrolysis, chemical deposition from vapour phase, sol-gel method [8–10]. These methods are used for obtaining thin SnO_2 films of high defectness and as a result of high conductivity.

Free electrons presence in them secures the surface plasmon resonance (SPR) effects developing. The surface plasmons excitation by electromagnetic radiation (EM) is specific for nanosized structures, containing nanoparticles (NPs) of noble metals and may be registered by the plasmon adsorption in visible, nearest UV and IR wave length range [11]. The spectral and angular SPR characteristics of nanostructured metal-dielectric films are very sensitive to the dielectric permittivity variation of the contacting with them outer medium [12]. This is widely used for monitoring. Addition of gold (Au) on the SnO_2 surface in [13] enhances a sensor best performance due to response (s) and time of response (t).

Previously in our [14] the SPR existence in SnO_2 films without Au NPs was shown. At the same work the effectiveness of modulation-polarisation spectroscopy method (MPS) was shown, as an alternative method for diagnostics and characterization of SnO_2 films. The present work is a continuation of SnO_2 films characterization by MPS method aiming the determination of optimal resonance-optical SPR parameters in dependence on the resonance type (localized or polariton one) and also the structure morphology specificity aiming future application in sensors.

20.2 Samples and Experimental Details

Samples for the investigation were prepared by the technique described in detail in [15]. Bis(acetylacetonato)dichlorotin (BADCT) was used as a tin dioxide precursor [16]. Freshly prepared BADCT was dissolved in acetone at different concentrations, then equal volumes of each solution were mixed with the same volumes of polyvinylacetate (PVAC) solutions in acetone prepared at different concentrations. The mixtures were then sprayed onto the microscope cover glass of $22 \times 22 \text{ mm}^2$ size. Samples were kept at room temperature for about 15 min to allow the acetone

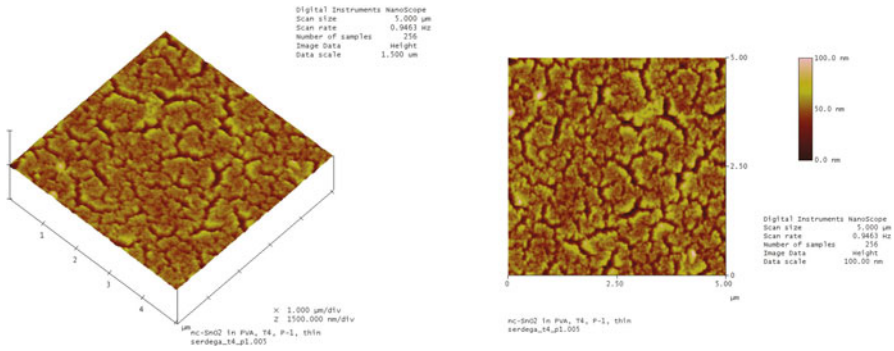


Fig. 20.1 AFM images of SnO₂ films

removing prior to annealing them at 600 °C for 6 h in air to achieve the thermal decomposition of the film organic components (BADCT and PVAC) and subsequent removing decay products. The organic components removing were confirmed by our thermogravimetric studies of the precursor [16] and by the data on the PVAC decomposition at temperatures above 200 °C, particularly in the presence of catalytic oxides (tin dioxide in our case). After annealing, the tin dioxide film was left on the substrate. PVAC was employed to structurize the film during removing its decay products. Force Microscopy (AFM) method (NanoScope IIIa, Digital Instruments). The tapping mode measurements were carried out with use of a silicon probe with nominal radius of about 10 nm. The AFM phase topology image of the sample T4.P1 (4 wt. % BADCT and 1 wt. % PVAC in the initial solution) is shown in Fig. 20.1a.

The optical scheme of experimental technique for spectral and angular SPR characteristics measurement based on the Kretschman [17] geometry and improved by the MPS method is described in details in [18]. The method is based on modulation of the EM radiation polarization. The idea of modulation is the periodical variation of probing radiation polarized state with constant intensity, frequency, phase and wave vector. The magnitude of the registered signal at the modulation frequency ($f = 60$ kHz) is equal to the intensities difference of the reflection coefficients s and p polarized radiations $\rho(\lambda, \theta) = R_s^2 - R_p^2$ – the polarization difference. According to the conventional terminology in polarimetry [19] this parameter is a Q -component of Stocks vector within the EM radiation which is reflected in this case by SnO₂ film fixed on a semicylinder surface and sensible to resonance. The phase locking detection of angular and spectral polarization characteristics increases the information ability of $\rho(\theta, \lambda)$ parameter, both due to the dynamic range extension of the measured quantity, and due to different signs of amplitude signals. The parameter ρ is more convenient in detection with high sensitivity to the peculiarities morphology of structure due to simultaneous measuring of R_s^2 and R_p^2 components under interaction between radiation and sample.

20.3 Results and Discussions

The angular characteristics of the internal reflection coefficients $R_s^2(\theta)$ and $R_p^2(\theta)$ and their polarization difference $\rho(\theta)$ at $\lambda = 500$ nm for SnO₂ films are shown at Fig. 20.2. For the incidence angles θ , more than the critical angle of total internal reflection $\theta_{cr} = 43^\circ$, the presented characteristics minima, are caused by the surface plasmons excitation for both *s*- and *p* polarized radiation.

The effectiveness of the resonance interaction of *s*-polarization in the present case exceeds over *p*-polarization (R_{sp}^p and R_{sp}^s are oscillators' forces, excited by corresponding polarized radiation). The negative values of $\rho(\theta)$ characterize the SnO₂ films structure as cluster one and nonuniform, which corresponds to the results of investigation of ultra thin and cluster gold films in [20].

In dependence on the structure peculiarities of the films studied, the SPR excitation is subdivided to several types: the excitation of the surface plasmon-polaritons on the infinite plane boundary of the metal-dielectric surface and the excitation of surface plasmons, localized on separate not interacting NPs or between NPs of metal due to dipole-dipole interaction. The spectral characteristics of the polarization difference $\rho(\lambda)$ at different incidence angles $\theta = 45^\circ, 55^\circ, 65^\circ$ are shown at the Fig. 20.3a for characterization of SnO₂ films, and SPR types definition. The complicated character of the parameter $\rho(\lambda)$ spectral contour is connected with different types of SPR in the films. The variable in signs form of curves $\rho(\lambda)$ caused by the resonance response from both polarizations at the phase-locked detection allows to interpret each extremum as a result of the resonant excitation of the surface plasmons of different nature.

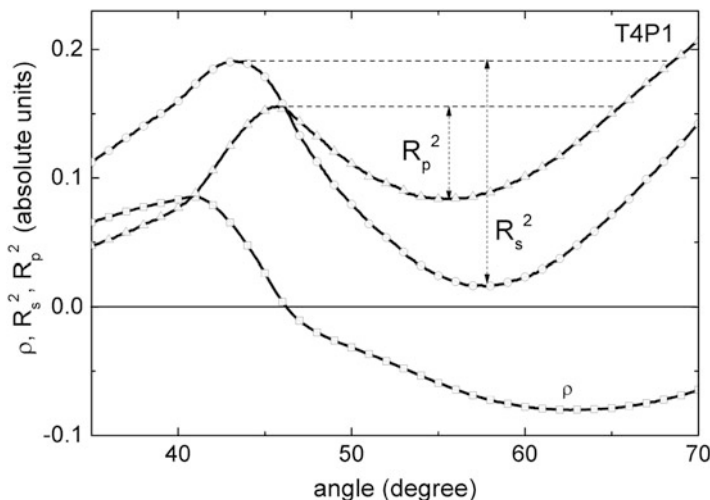


Fig. 20.2 Angular dependences of the internal reflection coefficients $R_s^2(\theta)$, $R_p^2(\theta)$ and polarization difference $\rho(\theta)$ at $\lambda = 500$ nm

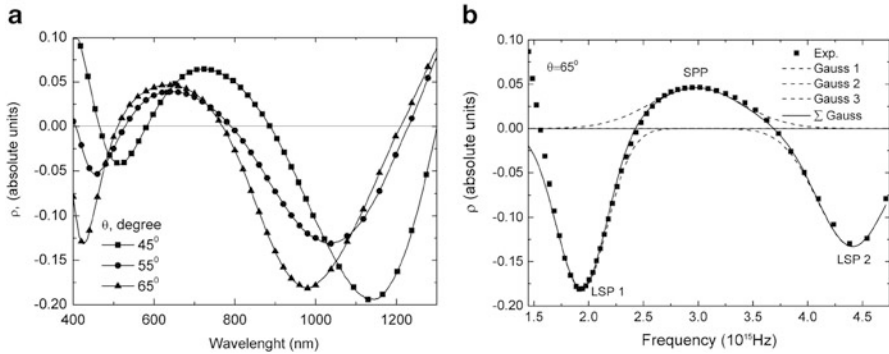


Fig. 20.3 (a) – spectral dependences of polarization difference $\rho(\lambda)$ for SnO₂ films at incident angles of $\theta = 45$ (square), 55 (circle), 65 (triangle), degrees. (b) – frequency dependence of polarization difference $\rho(\omega)$ at $\theta = 65^\circ$ (marks) recalculated from the corresponding dependence of $\rho(\lambda)$ in comparison with the Gaussian distribution function (solid line) expanded into components (dashed line)

The negative sign extrema in $\rho(\lambda)$ spectra are conditioned by the resonant excitation of the localized surface plasmons in a short wavelength region ($\lambda_{\text{LSP1}} \sim 500$ nm) on clusters or surface structure inhomogeneity, but in a long wavelength region ($\lambda_{\text{LSP2}} \sim 1000$ nm) between clusters due to electrodynamic/ dipole-dipole interaction. In both cases, the simultaneous resonant interaction of both s - and p -polarized radiation with SnO₂ film occurs. Extrema with positive $\rho(\lambda)$ values at $\lambda_{\text{SPP}} \sim 650$ nm are conditioned by the surface plasmon-polariton excitation in the interface film-air, consequently, as a result of resonant interaction only for p -polarized radiation. It is to be mentioned, that the “blue shift” occurs for corresponding extrema, which is conditioned by the considerable thickness $d = 230\text{--}400$ nm of the SnO₂ films. Such peculiarities of $\rho(\lambda)$ curves are specific for cluster type and inhomogenous structure films [21].

Aiming the definition of every SPR parameters, the $\rho(\lambda)$ characteristics were studied by means of Gaussian functions approximation. As a result, the amplitude and relaxation resonance parameters were obtained. The frequency dependence of $\rho(\omega)$ of one of $\rho(\lambda)$ curves at $\theta = 65^\circ$ was shown at Fig. 20.3b. The following principal frequencies and FWHM parameters (full width at a half maximum) are obtained: $\omega_{\text{LSP1}} = 1.9 \times 10^{15}$ Hz, $\gamma_{\text{LSP1}} = 0.73 \times 10^{15}$ s⁻¹; $\omega_{\text{SPP}} = 2.86 \times 10^{15}$ Hz, $\gamma_{\text{SPP}} = 0.994 \times 10^{15}$ s⁻¹; $\omega_{\text{LSP2}} = 4.43 \times 10^{15}$ Hz, $\gamma_{\text{LSP2}} = 0.544 \times 10^{15}$ s⁻¹. In all cases considered the surface plasmons excitation has non radiative nature and needs to secure phase-synchronous conditions, when both frequency (ω) and wave vector (k) of light excitation matches to those of the surface plasmon’s frequency and wave vector.

The resonances frequencies values, obtained from the components’ extrema (dash lines), both with the wave vectors magnitudes, considering the incidence angle (θ), permit to build the dispersion characteristics $\omega(k)$ of the surface plasmons (Fig. 20.4). The dispersion curves shape, their position in $\omega(k)$ coordinates, and

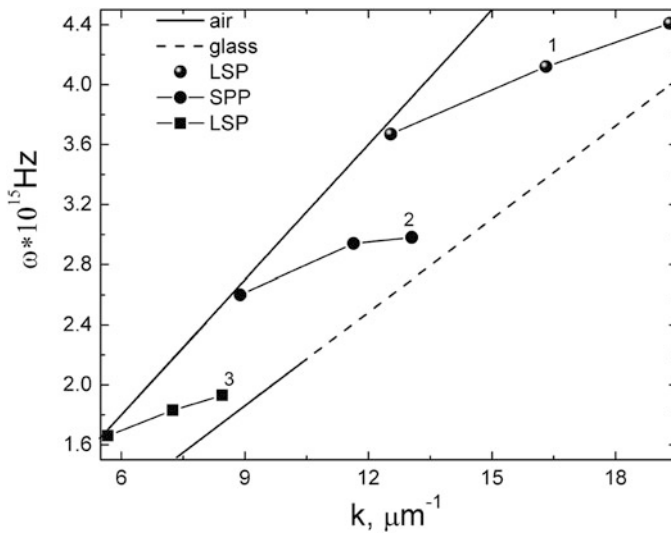


Fig. 20.4 Dispersion characteristics $\omega(k)$ of surface plasmons localized on isolated clusters (1), between clusters caused by dipole fields' interactions (3), and surface plasmon-polaritons (2) for SnO_2 films

also AFM images, makes it possible to identify two of them, correspondingly, as excitation of the surface plasmons, localized on separate, not interacting clusters, and interclusters interaction and the third – the excitation of surface plasmon-polaritons.

The angle dependencies of the relaxation parameters, γ , connected with SPR type is presented at Fig. 20.5. It is evident, that the biggest γ values corresponds to the surface plasmon-polariton excitation. According to the least γ parameter value rule, the SPR intercluster interaction dependence is the most appropriate for sensors applications. It is evident, the parameter value $\gamma_{\text{LSP2}} = 0.472 \times 10^{15} \text{ s}^{-1}$ at the angle $\theta = 45^\circ$, provides the maximum $\rho(\lambda)$ characteristic slope. It's shift as a result of the film interaction with an external detected medium, secures the maximum effectiveness in the sensors applications.

20.4 Conclusions

The characterization of resonant-optical parameters and morphology features of sensor – SnO_2 films is fulfilled by modulation – polarization spectroscopy method. Two SPR types are registered, which are conditioned both by the surface plasmon-polaritons excitation and localized surface plasmons on separate not interacting clusters and between clusters due to dipole interaction. The polarization analysis of SnO_2 research showed the inhomogeneity and cluster type of the structure

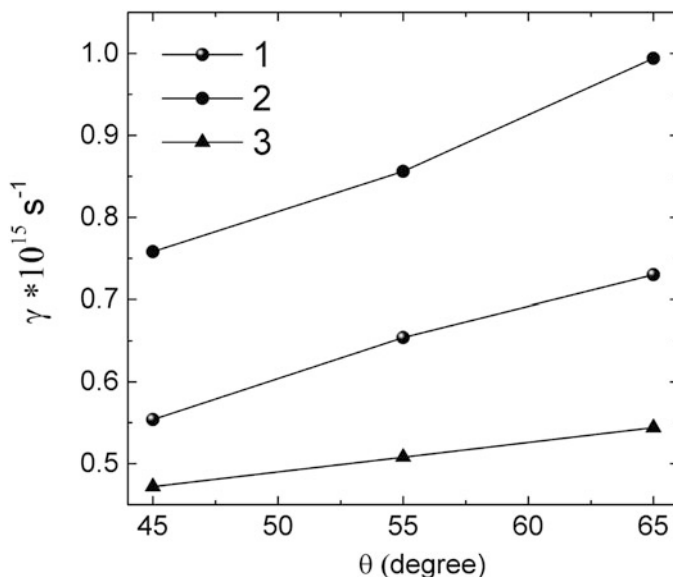


Fig. 20.5 Angular dependences of the relaxation parameters of SPR characteristics for SnO₂ films

morphology. The optimal resonance-optical parameters were obtained for SPR intercluster inter action, which supposes and secures their angular and spectral characteristics maximum effectiveness in the sensors applications.

References

1. Batzill M, Diebold U (2005) The surface and materials science of tin oxide. *Prog Surface Sci* 79:47–154
2. Ganesh EP, Kajale DD, Chavan DN, Pawar NK, Ahire PT, Shinde SD, Gaikwad VB, Jain GH (2011) Synthesis, characterization and gas sensing performance of SnO₂ thin films prepared by spray pyrolysis. *Bull Mater Sci* 34(1):1–9
3. Ginley DS, Hosono H, Paine DC (2010) *Handbook of transparent conductors*. Springer, New York
4. Ryabtsev SV (2011) Electrical and optical properties of various tin oxide nanoforms. Doctor's dissertation Theses, Voronezh
5. Lin J, Peng Zh, Xiang Ch, Ruan G, Yan Zh, Natelson D, Tour JM (2013) Graphene nanoribbon and nanostructured SnO₂ composite anodes for lithium ion batteries. *ACS Nano* 7(7):6001–6006
6. Xia G, Li N, Li D, Liu R, Wang Ch, Li Q, Lü X, Spindelov JS, Zhang J, Wu G (2013) Graphene/Fe₂O₃/SnO₂ ternary nanocomposites as a high-performance anode for lithium ion batteries. *ACS Appl Mater Interfaces* 5(17):8607–8614
7. Wu R, Chen X, Hu J (2012) Synthesis, characterization, and biosensing application of ZnO/SnO₂ heterostructured nanomaterials. *J Solid State Electrochem* 16(5):1975–1982. doi:10.1007/s10008-011-1590-6

8. Joshi BN, Yoon H, Yoon SS (2013) Structural, optical and electrical properties of tin oxide thin films by electrostatic spray deposition. *J Electrostat* 71(1):48–52
9. Inchidjuy P, An KS, Pukird S (2013) Growth and characterization of SnO₂ nanostructures by vapor transport technique. *Adv Mater Res* 677(3):94–97
10. Gnanam C, Rajendran V (2010) Synthesis of tin oxide nanoparticles by sol-gel process: effect of solvents on the optical properties. *J Sol-Gel Sci Technol* 53(3):555–559
11. Maier SA (2007) *Plasmonics: fundamentals and applications*. Springer, New York, p 221
12. Orfanides P, Buckner TF, Buncick VC, Meriaudeau F, Ferrell TL (2000) Demonstration of surface plasmons in metal island films and the effect of the surrounding medium – An undergraduate experiment. *Am J Phys* 68(10):936–942
13. Bakrania SD, Wooldridge MS (2010) The effects of the location of Au additives on combustion-generated SnO₂ nanopowders for CO gas sensing. *Sensors* 10(7):7002–7017
14. Grinevich VS, Filevska LM, Matyash IE, Maksimenko LS, Mischuk ON, Rudenko SP, Serdega BK, Smyntyna VA, Ulug B (2012) Surface plasmon resonance investigation procedure as a structure sensitive method for SnO₂ nanofilms. *Thin Solid Films* 522:452–456
15. Filevskaya LN, Smyntyna VA, Grinevich VS (2006) Morphology of nanostructured SnO₂ films prepared with polymers employment. *Photoelectronics* 15:11–14
16. Ulug B, Türkdemir HM, Ulug A, Büyükgüngör O, Yücel MB, Grinevich VS, Filevskaya LN, Smyntyna VA (2010) Structure, spectroscopic and thermal characterization of bis(acetylacetonato)dichlorotin(IV) synthesized in aqueous solution. *Ukr Chem J* 7:12–17
17. Kretzschmann E, Raether H (1968) Radiative decay of non-radiative surface plasmons by light. *Z Naturforsch A* 23:2135
18. Berezinsky LJ, Maksimenko LS, Matyash IE, Rudenko SP, Serdega BK (2008) Polarization modulation spectroscopy of surface plasmon resonance. *Opt Spectrosc* 105(2):257–264
19. Gerrard A, Burch JM (1975) *Introduction to matrix methods in optics*. Wiley, London
20. Serdega BK, Rudenko SP, Maksimenko LS, Matyash IE (2011) Plasmonic optical properties and the polarization modulation technique. In: Mishchenko MI, Yatskiv YS, Rosenbush VK, Videen G (eds) *Polarimetric detection, characterization and remote sensing*. Springer, Dordrecht, pp 473–500
21. Vozny AA, Stetsenko MO, Kosyak VV, Maksimenko LS, Opanasyuk AS, Serdega BK (2015) Detection of structural characteristics of nanosized Sn_xS_y film by the modulation-polarization spectroscopy of plasmon resonance. *Proc NAP 4, 02 NAESP06*